



Microstructural analysis of neutron-irradiation induced changes in polyester fibre studied using EPMA

Biswajit Mallick^{1*}, Ramesh Chandra Behera², Simanchal Panigrahi¹, Tanmaya Badapanda¹, Biswanath Parija¹, Banita Behera¹, Manas Panigrahi¹ and Madhumita Sarangi²

¹Department of Physics, National Institute of Technology, Rourkela-769 008, Orissa, India

²Department of Metallurgical and Materials Engineering, National Institute of Technology, Rourkela-769 008, Orissa, India

E-mail : bmallick_iopb@scientist.com

Abstract : Electron microscopy is an important characterization technique for the study of textile fibre as it gives more information on fabric wear, nature of fibre fracture, chemical degradation, abrasion, fatigue and many others. Electron Probe Micro Analyzer (EPMA) micrographs of virgin and some neutron-irradiated samples (graphite coated) are discussed. The filament diameter, D , of virgin PET fibre obtained from EPMA study was 12.5 μn . The surface topography of single filament distinctly reveals the core and sheath parts of the filament. The core diameter of the virgin fibre was estimated to be 1.43 μm . The fibre irradiated at fluence 1×10^{12} n/cm² shows radiation induced sphere like polymer balls or spherulites of diameter 2.27 μm in the expanded core region. Due to irradiation, the sheath area crosslinks with expanded core region, which may be responsible for increase of strength and hardness of the polymer materials. Moreover, the micrograph at 3000 X magnifications clearly shows that there is no preferred orientation of the polymer in any direction confirming the isotropic nature of the sample.

Keywords : Polyethylene terephthalate, neutron fluence, EPMA.

PACS Nos. : 81.05.Lg, 61.82.Pv, 61.72.-y

1. Introduction

In general, the modification of polymer properties under ionizing radiation [1] is a subject of great interest due to the increasing uses of polymers in various fields like hard radiation environments encountered in nuclear power plants, space-crafts industry, sterilization irradiators, high energy particle accelerators *etc.* Among the synthetic polymers, polyethylene terephthalate (PET) or commonly known as polyester, is significant because of its mechanical strength, inertness to chemical action and resistance to thermal environment. Again, PET fibres are mainly used in textile industry

*Corresponding Author

[2,3]. Apart from that, it is also used in the field of surgical polymeric textiles [4,5], composites [6,7], nanocomposites [8], conducting polymer [9], electroactive polymer [10] etc. Polyesters are mainly cross-linked when irradiated. Cross-linking of macromolecules is facilitated by the appearance of free radicals when hydrogen is extracted from the main chain of carbon atoms and transfer of the unpaired electron along the chain. This increases the probability of its proximity to a similar free radical of another macromolecule. At a definite stage of irradiation, the polymer molecules are cross-linked or chemically bonded into a common structure. Then this irradiated polymer possesses the improved mechanical (modulus, hardness, strength etc.), electrical, thermal and chemical properties. Neutron irradiation [11–13] significantly changes the properties of polymeric materials by the displacement of lattice atoms and the generation of helium and hydrogen by nuclear transmutation.

When fast neutron undergoes an interaction, it does so with a nucleus of the absorbing-material; as a result, materials gain enough energy; hence modification in the material properties takes place. In a head-on collision with hydrogen or hydrogen like materials, the neutron transfers all its kinetic energy in a single encounter. The maximum kinetic energy of the recoil nucleus $(E_R)_{\max}$ can be expressed as

$$(E_R)_{\max} = \frac{4A}{(1+A)^2} E_n,$$

where A is the mass of the target nucleus per neutron mass and E_n the kinetic energy of incident neutron. Another important aspect is that the fast neutron can produce dense ionization at deep levels in the material. Such an effect is difficult to be obtained by direct ionization radiation like protons, because it will only produce ionization at the spot, receiving radiation.

2. Experimental

Partially oriented yarn (POY) of polyethylene terephthalate (PET) fibre used for our investigation was obtained from a commercial polyester plant. The PET fibre used for the irradiation study is of bright yarn type with raw denier (weight in gram of 9000 meter of yarn) value of 78.2 with 36 filaments. The bright yarn with denier per filament (*dpf*) value 2.17 was used for the above irradiation study.

The neutron radiation source used for the present irradiation study was produced from an Am-Be source by (α, n) type nuclear reaction. Taking Am^{241} as a α -source of energy (5.48 MeV) an experimental neutron yield of about 70 neutrons per 10^6 α 's is generally obtained from a beryllium target. A neutron beam of energy 4.44 MeV and flux 2.2×10^6 n/cm²/s from an Am-Be source was used. According to Nereson and Darden [14] the average energy spread over the 3- to 12-MeV energy range is approximately 10 percent and the over-all accuracy of the results is ± 10 percent or better. Spread in neutron energy around 4.44 MeV is approximately 44 keV. The PET

fibre samples are irradiated in air at the atmospheric pressure in the temperature range of 22–27°C for different exposure times to get three different fluences viz. : 1×10^9 n/cm² (II), 5×10^{10} n/cm² (III) to 2×10^{11} n/cm² (IV). In the present investigation, surface of the virgin and irradiated PET fibre samples were characterized by Electron Probe Micro Analyzer (EPMA).

A JEOL JXA-8100, JEOL Co, Japan make EPMA (Accelerating voltage = 0.2 to 30 kV; probe current = 10^{-12} to 10^{-5} A with probe current stability = $\pm 0.5 \times 10^{-3}$ /h), was used to investigate the topography of graphite-coated single PET fibre. An electron beam of 5 kV and 41 μ A has been used for EPMA analysis of fibre samples in the microscopy mode.

3. Results

The scanning electron microscope (SEM) and electron probe micro analyser (EPMA) are important in the study of textile fibres as they give more information on fabric wear, nature of fibre fracture, chemical degradation, abrasion, fatigue and many others. The EPMA micrographs of virgin and some neutron-irradiated samples (graphite coated) at two different magnifications (1500 X and 3000 X) are shown in Figure 1. The filament diameter, D , of virgin PET fibre obtained from EPMA study (Figures 1(a) and (b)) was 12.5 μ m. The micrographs of surface topography of single filament distinctly reveals the core (internal part of fibre) and sheath (covering part of fibre) parts of the filament. The core diameter of the virgin fibre was estimated to be 1.43 μ m. It is observed that the filament diameter increases due to fibre shrinkage in linear direction because of neutron irradiation (radiation heating). The fibre irradiated at fluence 5×10^{10} n/cm² (sample III) produces a filament diameter of 15 μ m (Figure 1(c)). It is also seen that, the core diameter increases to 3 μ m with neutron fluence whereas filament-diameter remains at 15 μ m. The fibre irradiated at fluence 1×10^{12} n/cm² shows radiation induced sphere like polymer ball or spherulites [15] of diameter 2.27 μ m in the expanded core region. Due to irradiation, the sheath area crosslinks with expanded core region, which may be responsible for increase of strength and hardness of the polymer materials. Moreover, the micrograph at 3000 X magnifications clearly shows that there is no preferred orientation of the polymer in any direction confirming the isotropic nature of the sample. This was also confirmed in an earlier study using X-ray diffraction, SEM and Micro-Raman techniques [13,16].

4. Conclusion

The EPMA micrograph of virgin (sample-I) and 4.44 MeV fast neutron irradiated PET fibres were analyzed. From the micrograph analysis an interesting thing observed when fibre irradiated at fluence 1×10^{12} n/cm² shows radiation induced sphere like polymer ball or spherulites of diameter 2.27 μ m in the expanded core region. Due to irradiation, the sheath area crosslinks with expanded core region, which may be responsible for

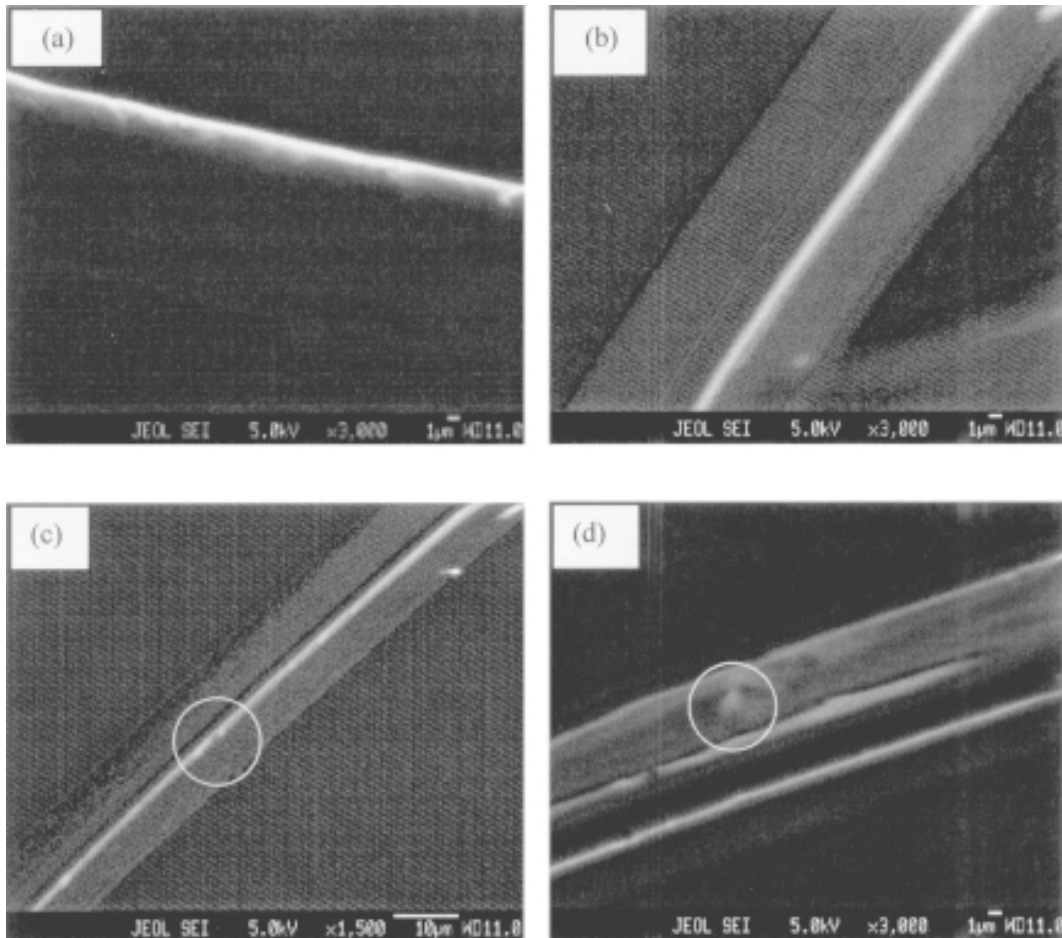


Figure 1. EPMA micrograph : (a) virgin fibre (sample-I), (b) sample (III) irradiated at 5×10^{10} n/cm², (c) sample (IV) irradiated at 1×10^{12} n/cm² and (d) sample (IV) showing formation of spherical particles.

increase of strength and hardness of the polymer materials. Moreover, the micrograph at 3000 X magnifications clearly shows that there is no preferred orientation of the polymer in any direction confirming the isotropic nature of the sample. Again the cross-linked fibre (*i.e.* sample-IV) is more useful for textile applications and development of polymer composite materials.

Acknowledgment

Authors would like to thank Dr. B K Mishra (Director) and Dr. B K Mohapatra of the Regional Research Laboratory, Bhubaneswar, for providing EPMA facilities.

References

- [1] J Davenas, I Stevenson, N Celette, S Cambon, J L Gardette, A Rivaton and L Vignoud *Nucl. Instrum. Meth.* **B191** 653 (2002)

- [2] T Patel and S Bal *Polym. J.* **33** 121 (2001)
- [3] N V Bhata and S G Naik *Textile Res. J.* **54** 868 (1984)
- [4] L M Ferreira, M H Casimiro, C Oliveira, M E Cabeco Silva, M J Marques Abreu and A Coelho *Nucl. Instrum. Meth.* **B191** 675 (2002)
- [5] M D Phaneuf, S A Berceli, M J Bide, W C Quist and K W LoGerfo *Biomaterials* **18** 755 (1997)
- [6] S Fu, P Wu and Z Han *Compos. Sci. Technol.* **62** 3 (2002)
- [7] Z-Ming Li, X-Bin Xu, Ai Lu, K-Zhi Shen, Rui Huang and M-Bo Yang *Carbon* **42** 428 (2004)
- [8] J-Hae Chang, S J Kim, Y L Joo and S Im *Polymer* **45** 919 (2004)
- [9] R Mishra, S P Tripathy, D Sinha, K K Dwivedi, S Ghosh, D T Khathing, M Muller, D Fink and W H Chung *Nucl. Instrum. Meth.* **B168** 59 (2000)
- [10] B Mallick, T Patel and R C Behera *WW-EAP Newsletter (NASA)* **6** 18 (2004)
- [11] A K Srivastava and H S Virk *Radiat. Phys. Chem.* **59** 31 (2000)
- [12] W M Abou Taleb, N K Madi, M E Kassem and A M El-Khatib *Radiat. Phys. Chem.* **47** 709(1996)
- [13] B Mallick, R C Behera and T Patel *Bull. Mater. Sci.* **28** 593 (2005)
- [14] N Nereson and S Darden *Phys. Rev.* **94** 1678 (1954)
- [15] I I Perepechko *An Introduction to Polymer Physics* (Moscow : Mir Publishers) **52** (1981)
- [16] B Mallick, T Patel and R C Behera *Indian J.Phys.* **80** 621 (2006)