

Positron annihilation lifetime measurements for C⁵⁺ ion irradiated Makrofol-N polycarbonate

Rajesh Kumar^{1*}, B K Nath², D Das² and Rajendra Prasad¹

¹Department of Applied Physics, Z H College of Engineering & Technology,
Aligarh Muslim University, Aligarh-202 002, Uttar Pradesh, India

²Inter University Consortium for DAE Facilities, Kolkata Centre, Kolkata-700 091, India

E-mail rajeshjrf2001@yahoo.com

Abstract Makrofol-N is the polycarbonate widely used in nuclear research, nuclear filters and in other applications. Latent ion tracks produced in the polymers due to the damage produced by the passage of Swift Heavy Ions contain amorphous material with highest degree of disorder, changing the free volume properties which have strong correlation with the macroscopic properties of the material. Positron Annihilation Lifetime Spectroscopy (PALS) provides direct information about the dimension, content and hole size distribution of free volume in polymers. The effect of irradiation of C⁵⁺ 70 MeV ions on Makrofol-N polycarbonate by Positron Annihilation Lifetime Spectroscopy (PALS) is reported here. PALS provides a non-destructive and non-interfering probe, having high detection efficiency for free volume hole properties. From the o-Ps lifetime, mean free volume, radius and average free volume have been obtained.

Keywords Makrofol-N polycarbonate, C⁵⁺ ion irradiation, positron lifetime, ion beam modification

PACS Nos. 42.88+h, 78.70.Bj, 71.20.Rv

1. Introduction

Polycarbonate (PC), or specifically polycarbonate of bisphenol A, is an amorphous polymer with attractive engineering properties, including high impact strength, low moisture absorption, good dimensional stability and high light transmission. Polycarbonate gets the name from the carbonate groups in its back bone chain and is called bisphenol A PC as it is made from bisphenol A and phosgene. It has been widely used in heavy ion research such as composition of cosmic rays, heavy ion nuclear reactions, radiation dose due to heavy ions damage in polymeric materials as latent tracks along their path due to dissociation of valence bonds, cross linking and formation of free radicals [1]. These ion tracks contain amorphous material with highest degree of disorder. The damage results into the change of free volume properties of the material which have strong correlation with its macroscopic properties [2]. Positron Annihilation Spectroscopy (PAS) has emerged as a unique and potent probe for characterizing the free volume properties of polymers [3]. In PAS the positron is used as a nuclear probe which is repelled by the ion cores and preferentially localized in the atomic size free-volume holes [4] of a polymeric material.

Therefore, the positron and positronium (Ps) annihilation signals are found to be contributed mainly from the free volume holes in the polymer. Ps atom has two spin states : para-positronium (p-Ps) having spin zero (lifetime in vacuum 125 ps) and ortho-positronium (o-Ps) having spin one (lifetime in vacuum 142 ns). o-Ps lifetime is reduced due to interaction of o-Ps with electrons from surrounding matter (pick off annihilation) and decays in two gamma rays. In polymers three positron lifetimes (τ_1, τ_2, τ_3) are often found which range from 100 ps to 5 ns. These lifetimes from shortest to longest are believed to be due to the self annihilation of p-Ps, the annihilation of free positron and the pick off annihilation of o-Ps respectively. Currently PAS has been mainly developed in monitoring the o-Ps (a triplet state) annihilation lifetimes (PAL) for polymeric applications. o-Ps lifetime and its probability are related to the free volume size, fraction and distribution.

2. Experimental details

Makrofol-N PC films (40 μm) obtained from Bayer AG, Germany, were irradiated with C⁵⁺ ions of 70 MeV at the fluence of 10^6 ions/cm² from 15 UD Pelletron accelerator at Nuclear Science Centre, New Delhi in General Purpose Scattering Chamber (GPSC) beam line. A 5 cm \times 5 cm sample was mounted on a

*Corresponding Author

target ladder and the chamber was evacuated to 10^{-6} torr. PAL measurements were made at Inter University Consortium for DAE Facilities, Kolkata Centre. A specially designed $5 \mu\text{Ci } ^{22}\text{Na}$ source deposited on a rhodium foil was sandwiched between the stacks of ten layers of polycarbonate film. The thickness of the samples is adequate to absorb more than 99% of positrons emitted. Fast-fast coincidence spectrometer which entails monitoring the signal (1.28 MeV gamma ray from positron decay of the source as start time and 0.511 MeV gamma ray from the positron annihilation in the material sample under study as the end time), was used for recording the PAL spectra. BaF_2 scintillators coupled to Phillips XP2020 photomultipliers were used. ORTEC Constant Fraction Differential Discriminators were used for selecting energy and providing time signals to Time to Amplitude Converter. The time resolution (FWHM) of prompt spectra was 280 ps.

3. Data analysis of PAL spectra

PAL spectra were analyzed by finite term lifetime analysis using PATFIT-88 [5] program. It decomposes a PAL spectrum into 2–5 terms of negative exponentials. In polymers 3 lifetime results give the best χ^2 (< 1.1) and most reasonable standard deviations [6]. o-Ps annihilation in the spherical free volume is described by simple quantum mechanical model of spherical potential well with an electron layer of thickness ΔR . The results of o-Ps lifetime (τ_3), the longest lifetime due to o-Ps annihilation were employed to obtain the mean free volume hole radius by the following semi-empirical equation [7].

$$\tau_3 = \frac{1}{\lambda_3} = \frac{1}{2} \cdot \frac{R}{R_0} + \frac{1}{2\pi} \sin\left(\frac{2\pi R}{R_0}\right)$$

where τ_3 and R (hole radius) are expressed in ns and \AA respectively. R_0 equals $R + \Delta R$ where ΔR is the fitted empirical layer thickness ($= 1.66 \text{\AA}$). The micro-void volume (V_f) is given by $\frac{4}{3} \pi R^3$.

4. Results and discussion

A lifetime spectra of unirradiated and irradiated PC are shown in Figure 1. From the analyses of lifetime spectra after source correction by PATFIT-88 computer code, the lifetime and intensity of three components, radius and free volume were obtained for unirradiated and irradiated samples and are presented in Tables 1 and 2.

In the PAL spectra it is the o-Ps lifetime which directly correlates to the free volume hole size [8]. The intensity of this component contains information about free volume hole concentration. When a swift heavy ion is bombarded on the polymer, the ion energy is transferred to atoms in the polymer chain in a very short time and in a very small volume surrounding ion track. According to thermal spike model, large amount of energy transfer results into the breakage/rearrangement of bonds

and production of excited and ionized species which are responsible for the structural changes in the material resulting

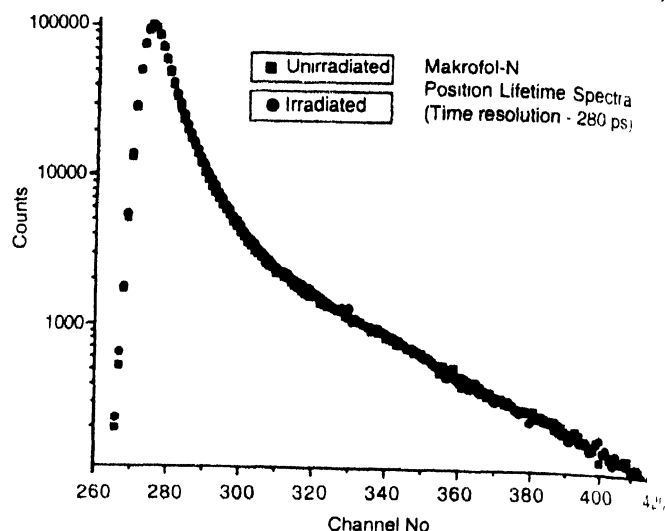


Figure 1.

into the distribution of energy imparted to the material. Thus the energy imparted to the material is distributed increasing the free volume. It is also possible that the energy is utilized in overcoming the van der Waals forces and creating new voids. At the low dose of 10^6 ions cm^{-2} the change in o-Ps lifetime is nominal. At the low dose the halo (diameter of the order of 100–1000 nm) which surrounds the tracks (diameter of the order of

Table 1. Lifetime and intensities of unirradiated and irradiated Makrofol-N polycarbonate

Sample	τ_1 (ns)	I_1 (%)	τ_2 (ns)	I_2 (%)	τ_3 (ns)	I_3 (%)
Unirradiated	0.14	29.52	0.38	45.91	2.20	24.56
Irradiated	0.16	31.96	0.40	43.14	2.25	24.89

Table 2. The lifetime parameters of o-Ps and radius of free volume hole in Makrofol-N

Sample	τ_3 (ns)	I_3 (%)	R (\AA)	V_f (\AA^3)
Unirradiated	2.20 ± 0.01	24.56 ± 0.14	3.04	117.70
Irradiated	2.25 ± 0.01	24.89 ± 0.19	3.08	122.43

1–10 nm) plays an important role. The halo is created by δ electrons which have a broad spectrum of kinetic energy and trigger considerable ionization on their own. The nominal effect of irradiation may be due to the fact that the electronic collision cascade (δ electrons) which spreads out rapidly around the track, does not alter the microstructure of the polymer considerably. Nominal change in the life time and free volume has been observed [9] in some polymers due to irradiation by oxygen ions.

In the present study, the average free volume of the microvoids for unirradiated Makrofol-N is computed to be 117.70\AA^3

After irradiation with C^{5+} the volume becomes 122.43 \AA^3 showing a change of 4%.

Acknowledgments

Sincere thanks are due to Dr. A K Sinha, Director IUC-DAEF, Kolkata for providing PAL facilities and constant encouragement. The authors wish to thank Dr. D K Awasthi and staff of Nuclear Science Centre, New Delhi during irradiation. We are also grateful to Dr. Y K Vijay for fruitful discussions.

References

- [1] H Myler, Xu X L, M R Coleman and P J Simpson *J Polym Sci B Polym Phys* **36** 2413 (1998)
- [2] J D Ferry *Viscoelastic Properties of Polymers* (3rd ed) (New York John Wiley & Sons Inc) (1980)
- [3] Y C Jean *Positron Spectroscopy of Solids* (eds) A Dupasquier and A P Mills (Jr) (Amsterdam IOS Pub) 563 (1995)
- [4] D M Schrader and Y C Jean (eds) *Positron and Positronium Chemistry, Studies in Physical and Theoretical Chemistry* (Amsterdam Elsevier) vol. **57** (1988)
- [5] P Kirkegaard, N J Pedersen and Eldrup *PATFIT-88 A data processing system for positron annihilation spectra for mainframe and personal computers* (Roskilde, Denmark : Riso National Laboratory) (1989)
- [6] Y C Jean and G H Dai *Nucl Inst Meth* **B79** 356 (1993)
- [7] H Nakanishi, S J Wang and Y C Jean *Positron Annihilation Studies of Fluids* (ed) S C Sharma (Singapore : World Sci Pub.) 292 (1988)
- [8] Y C Jean *3rd Int Workshop on Positron and Positronium Chemistry* 16 (1990)
- [9] Y K Vijay, S Wate, D K Awasthi, D Das and S Ghughre *Indian J Eng & Mat Sci* **7** 375 (2000)