



# Preparation, characterization and magnetic properties of hexagonal $Y_{1-x}Ce_xMnO_3$

S K Srivastava<sup>1</sup>, Manoranjan Kar<sup>2</sup> and S Ravi<sup>1\*</sup>

<sup>1</sup>Department of Physics, <sup>2</sup>Centre for Nanotechnology  
Indian Institute of Technology, Guwahati Guwahati-781 039, Assam India

E-mail sravi@iitgernet.in

**Abstract** Electron doped  $Y_{1-x}Ce_xMnO_3$  compounds were prepared for  $x = 0, 0.05, 0.10$  and  $0.15$  by solid state route. These samples were characterized by recording X-ray diffraction (XRD) pattern, Scanning Electron Micrographs and Energy Dispersive Spectrum (EDS) at room temperature. All the samples are essentially in single phase form with hexagonal structure and could be refined using  $P6_3cm$  space group. The typical lattice parameters are found to be  $a = b = 6.133\text{\AA}$  and  $c = 11.366\text{\AA}$  for  $Y_{0.9}Ce_{0.1}MnO_3$  sample. Temperature variations of ac susceptibility measurements down to 20K were carried out and they show that the Ce doped samples exhibit paramagnetic to ferromagnetic transition with onset temperature at around 100K followed by low temperature peak at around 28K, indicating the presence of competing magnetic interactions.

**Keywords** Electron doped manganites,  $Y_{1-x}Ce_xMnO_3$ , Ferromagnetism, ac susceptibility

**PACS Nos.** 75.47.Lx, 61.05.cp

## 1. Introduction

The rare earth perovskite manganites,  $(R_{1-x}A_x)MnO_3$  ( $R = La$ , Rare earth elements,  $A =$  Alkaline earth, Alkali elements) have been studied extensively due to their interesting electrical and magnetic properties including colossal magnetoresistive (CMR) behaviour [1-5]. Recently there are a few reports on the electron doped rare earth manganites, where there is a possibility of CMR due to double exchange interaction between  $Mn^{2+}$  ( $t_{2g}^3 e_g^2$ ) and  $Mn^{3+}$  ( $t_{2g}^3 e_g^1$ ) ions [6,7]. The  $La_{0.7}Ce_{0.3}MnO_3$  compounds exhibit transition from paramagnetic insulator (PMI) to ferromagnetic metallic state (FMM) along with CMR behaviour [6-11]. However it has been found that the observed CMR behaviour is mainly due to hole doping rather than electron doping, as a result of  $CeO_2$  impurity segregation and over oxidation. On the other hand, the electron doped  $Nd_{0.7}Ce_{0.3}MnO_3$  with  $Mn^{2+}/Mn^{3+}$

mixture could be prepared in single phase form, especially by depositing thin films and they exhibit FM transition around 60 K [6, 12-14]

The hexagonal  $\text{YMnO}_3$  is the well known A-type antiferromagnetic (AFM) material with transition temperature around 80K [15-17] Unlike other rare earth manganites, the hole and electron doping studies in  $\text{YMnO}_3$  are very limited To study the effect of electron doping and possible double exchange ferromagnetic interaction between  $\text{Mn}^{2+}$  and  $\text{Mn}^{3+}$  ions, we have prepared  $\text{Y}_{1-x}\text{Ce}_x\text{MnO}_3$  compounds for  $x = 0$  to 0.15 As the ionic sizes of Y and Ce are comparable unlike, the case of La & Ce, it could be possible to prepare single phase materials for a wide doping range In the present article, the preparation, characterization and magnetic properties of  $\text{Y}_{1-x}\text{Ce}_x\text{MnO}_3$  are presented

## 2. Experimental details

The  $\text{Y}_{1-x}\text{Ce}_x\text{MnO}_3$  ( $x = 0, 0.05, 0.10$  and  $0.15$ ) compounds were synthesized by solid state route The stoichiometric ratio of  $\text{Y}_2\text{O}_3$ ,  $\text{CeO}_2$  and Mn metal powder with 99.9% purity were weighed and mixed thoroughly under acetone The mixture was presintered at  $860^\circ\text{C}$  for 36 h with intermediate grindings The sintering in pellet form was carried out at  $1050^\circ\text{C}$  for 24 h, followed by sintering at  $1250^\circ\text{C}$  for over 50h in oxygen atmosphere Then the samples were subjected to hot pressing by applying a load of 10 ton at  $950^\circ\text{C}$  for 2h using a commercial hot press furnace The X-ray diffraction (XRD) patterns were recorded at room temperature using Bruker D8 Advance X-ray diffractometer by employing  $\text{CuK}_\alpha$  radiation Scanning Electron Micrographs were recorded at room temperature by using LEO Scanning Electron Microscope (SEM) Compositional analysis was carried out by employing SEM-EDS (energy dispersive spectrum) technique Temperature variation of ac susceptibility measurement was carried out by employing mutual inductance bridge method with an ac field amplitude of 60e and at 333Hz A commercial helium closed cycle

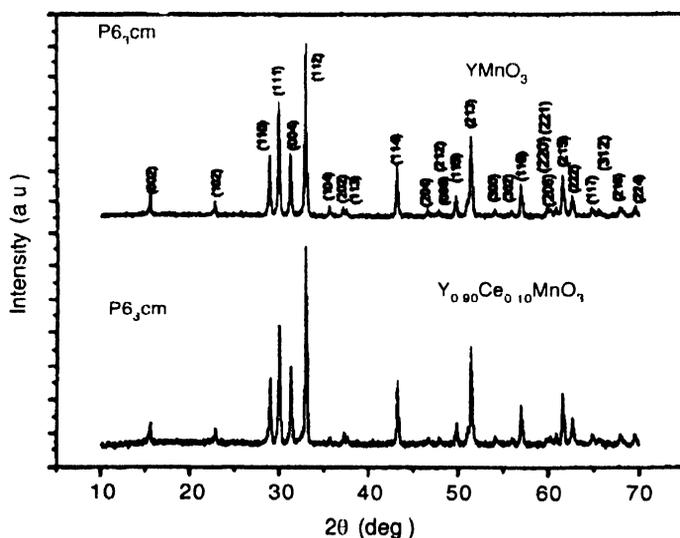
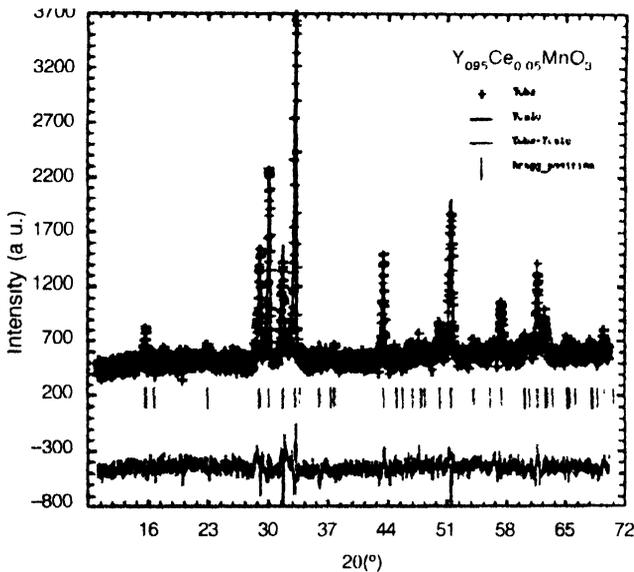


Figure 1. XRD patterns of  $\text{YMnO}_3$  and  $\text{Y}_{0.9}\text{Ce}_{0.1}\text{MnO}_3$

refrigerator cryostat equipped with a Lake Shore temperature controller has been used for temperature variation down to 20K.

### 3. Results and discussions

Typical XRD patterns for  $x = 0$  and  $x = 0.10$  are shown in Figure 1. All the observed peaks could be indexed to  $P6_3cm$  space group and hence the samples are essentially in single phase form. All the XRD patterns were analyzed using Fullprof program by employing Rietveld refinement technique [18]. Typical XRD pattern along with Rietveld refinement is shown in Figure 2 for  $x = 0.05$ . Here the experimental data are shown as crosses (+) and



**Figure 2.** XRD pattern along with refined data for the sample  $Y_{0.95}Ce_{0.05}MnO_3$ . Experimental data are shown as crosses (+) and calculated intensities are shown as solid lines. The bottom line represents the difference between measured and calculated intensities.

the calculated intensities are shown as solid lines. The bottom line represents the difference between measured and calculated intensities. The obtained lattice parameters are given in Table-1 and are comparable to those reported by Wood *et al* [16].

In polycrystalline materials, tiny crystals are arranged in random direction, the size of the crystals can be estimated from the width of the XRD patterns. The average crystal size depends upon the annealing temperature and doping concentrations and, under optimum preparation conditions; larger crystallite sizes are generally formed. In the present work, average crystallite size ( $S_c$ ) has been calculated using the Scherrer's formula [19]

$$S_c = k\lambda/\beta \cos\theta \quad (1)$$

where, constant 'k' depends upon the shape of the grain size (= 0.89, assuming the circular grain),  $\beta$  is full width at half maximum (FWHM) of intensity vs.  $2\theta$  profile, is the wavelength of the  $CuK_\alpha$  radiation and  $\theta$  is the Bragg's diffraction angle. The values are



Figure 6. shows the typical plots of  $\chi'$  versus temperature (T) for the samples  $x = 0.05$  and  $0.10$ . We can see that the samples exhibit upturn in susceptibility with onset temperature around 100K followed by sharp increase in susceptibility at low temperature.

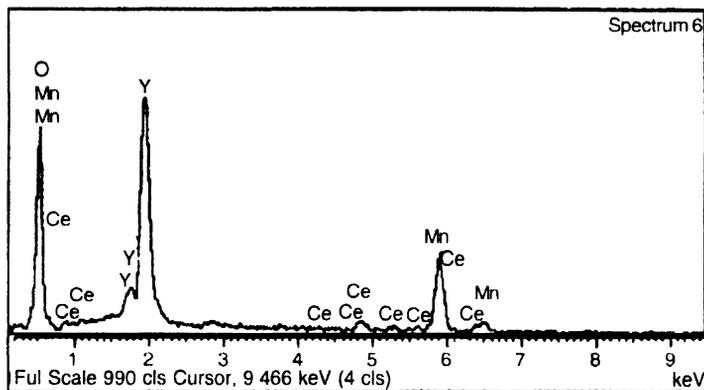


Figure 5. Typical SEM-EDS spectra for  $Y_{0.9}Ce_{0.1}MnO_3$  sample

In addition to that, they exhibit a sharp peak at 24K and 28 K for  $x = 0.05$  and  $x = 0.10$  samples respectively. The observed behaviour is comparable to that reported by Chen *et al* [20] on  $YMn_{1+x}O_3$  compound. The above observed FM behaviour can be explained on the basis of double exchange interaction between  $Mn^{2+}$  and  $Mn^{3+}$  ions. It is clear from the above observation that Ce plays the role of electron doping by creating a mixture of  $Mn^{2+}$  and  $Mn^{3+}$  ions. The appearance of low temperature peak indicates the presence of spin glass like behaviour due to competing magnetic interactions. The data in the high temperature region were fitted to the Curie Weiss law,

$$\chi' = \frac{C}{T - \theta_c} \quad (2)$$

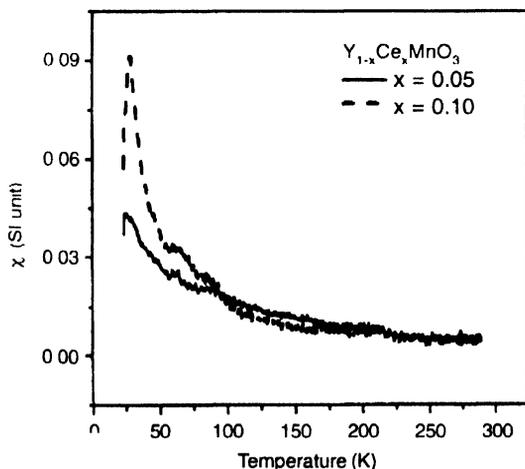


Figure 6. Temperature variation of inphase susceptibility ( $\chi'$ ) of  $Y_{1-x}Ce_xMnO_3$  samples for  $x = 0.05$  and  $0.10$ .

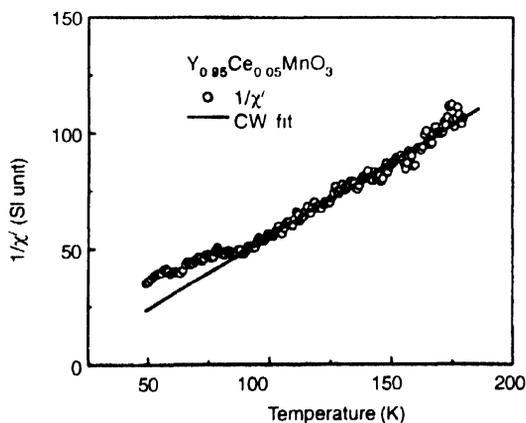


Figure 7.  $1/\chi'$  versus Temperature for the sample  $Y_{0.95}Ce_{0.05}MnO_3$ . Solid line represents the fit to the Curie-Weiss law.

Here  $\theta_c$  is the Curie temperature, C is the Curie constant and  $\chi'$  is the measured susceptibility. The typical  $1/\chi'$  versus T plot for  $x = 0.05$  is shown in Figure 7 and it exhibits a linear behaviour. The fitted data are shown as solid line. The Curie temperature obtained from the above fit is given in Table 1. The value of  $\theta$   $x = 0$  sample is found to be comparable to that reported by Munoz *et al* [21]. The Curie temperature for Ce doped compounds is found to be positive, which reveals the presence of ferromagnetic interaction.

#### 4. Conclusions

$Y_{1-x}Ce_xMnO_3$  compounds have been prepared essentially in single phase form for  $x = 0$  to 0.15. All the samples are found to be crystallized in hexagonal structure with  $P6_3cm$  space group. Increase in susceptibility magnitude, positive Curie temperature and FM like transition have been observed in Ce doped samples. The Curie temperature is found to be -ve for the parent  $YMnO_3$ . The observed magnetic behaviour suggests that there is a possibility of double exchange interaction between  $Mn^{2+}$  and  $Mn^{3+}$  ions due to electron doping. They also show the presence of spin glass like behaviour.

#### Acknowledgment

The authors are thankful to DST, New Delhi for financial support.

#### References

- [1] R von Helmolt, J Wecker, B Holzapfel, L Schultz and K Samwer *Phys Rev Lett* **71** 2331 (1993)
- [2] S Jin, T H Tiefel, M McCormack, R A Fastnacht, R Ramesh and L H Chen *Science* **264** 413 (1994)
- [3] A Asamitsu, Y Moritomo, Y Tomioka, T Arima and Y Tokura *Nature* **373** 407 (1995)
- [4] R Mahesh, R Mahendiran, A K Raychudhuri and C N R Rao *J Solid State Chem* **114** 297 (1995)
- [5] *Colossal Magneto-Resistance, Charge Ordering and Related Properties of Manganese Oxides* (ed) C N R Rao and B Raveau (Singapore: World Scientific) (1998)
- [6] P Mandal and S Das *Phys Rev* **B56** 15073 (1997)
- [7] J R Gebhardt, S Roy and N Ali *J Appl Phys* **85** 5390 (1999)
- [8] C Mitra, P Raychaudhury, J John, S K Dhar, A K Nigam and R Pinto *J Appl Phys* **89** 524 (2001)
- [9] R Ganguly, I K Gopalkrishnan and J V Yakhmi *Physica* **B275** 308 (2004)
- [10] Y G Zhao, R C Srivastava, P Fournier, V Smolyaninova, M Rajeswari, T Wu, Z Y Li, R L Greene and T Venkatesan *J Magn Magnet Mat* **220** 161 (2000)
- [11] T Yanagida, T Kanki, B Vilquin, H Tanaka and T Kawal *J Appl Phys* **97** 033905 (2005)
- [12] S Z Hang, S Tan, W Tong and Y Zhang *Phys Rev* **B72** 014453 (2005)
- [13] T Yanagida, T Kanki, B Vilquin, H Tanaka and T Kawal *J Appl Phys* **99** 053908 (2006)
- [14] T Yanagida, H Tanaka, T Kawal, E Ikenaga, M Kobata, J J Kim and K Kobayashi *Phys Rev* **B73** 132503 (2006)
- [15] W C Koehler, H L Yakel, E O Wollan and J W Cable *Phys Lett* **9** 93 (1964)
- [16] V E Wood, A E Austin, E W Collings and K C Brog *J Phys Chem Solids* **34** 859 (1973)
- [17] Z J Huang, Y Cao, Y Y Sun, Y Y Xue and C W Chu *Phys Rev* **B56** 2623 (1997)
- [18] R A Young "The Rietveld Method" *International Union of Crystallography* (New York: Oxford University Press) (1996)
- [19] A Taylor *X-ray Metallography* (New York: Wiley) (1961)
- [20] W R Chen, F C Zhang, J Miao, B Xu, L X Cao, X G Qiu and B R Zhao *J Phys Condens Matter* **17** 8029 (2005)
- [21] A Munoz, J A Alonso, M T Casias, M J Martinez-Lopez, J L Martinez and M T Fernandez *J Phys Condens Matter* **14** 3285 (2002)